

Research Article

Optical properties of $\text{In}_x\text{Ga}_{1-x}\text{As}$ quantum Wells Grown by Molecular Beam Epitaxial Technique

LaxmanSurvase^{A*}, SenMathew^B, Mahesh Gokhale^C and ManoharNyayate^D

^AShr. S.H. Kelkar College of Arts, Commerce and Science, Devgad. Dist- Sindhudurg.

^BCenter for High Technology Materials (CHTM) University of New Mexico (UNM).

^CTata institute of fundamental research Mumbai; India

^DB.N. Bandokar College; Thane, India

Accepted 15 Nov 2014, Available online 20 Dec 2014, Vol.4, No.6 (Dec 2014)

Abstract

The samples were grown on (001)-oriented GaAs substrates using molecular beam epitaxy system. The effect of change in the percentage of indium on the optical properties of $\text{In}_x\text{Ga}_{1-x}\text{As}$ quantum well structures is investigated using the temperature-dependent photoluminescence from 15 K to 300 K and Raman spectroscopy. The temperature-dependent integrated photoluminescence intensities of the samples reveal that the photoluminescence intensity is significantly enhanced by about 27 times at 15 K with respect to that at 300 K.

Keywords: $\text{In}_x\text{Ga}_{1-x}\text{As}$, quantum wells, photoluminescence, Raman spectroscopy.

1. Introduction

Optoelectronics based on very thin layers of semiconductor heterostructures, such as quantum wells (QWs), play an important role in many commercial applications. Currently InGaAs QW structures are used in opto electronic devices such as fiber optic communication [Devaux *et al* 1995], solar cell [Raisky *et al* 1998], infrared detectors [Levine 1993] or lasers. Semiconductor quantum structures are in common usage for optoelectronics as well as high-speed electronics. Electronic energy levels of quantum structures are important structural parameters because of their dependence on size, composition, strain, etc. A number of spectroscopic techniques photoluminescence (PL), photoluminescence excitation (PLE), and absorption have been in use to probe the electronic transitions. [Arora *et al* 2001]

Luminescence techniques belong to the most sensitive, nondestructive methods of analyzing semiconductor properties [Chen *et al* 2009].

2. Experimental Detail

All the samples were grown on (001)-oriented GaAs substrates using molecular beam epitaxy system DCA 450 model. As shown in the Fig. (1), the growth of $\text{In}_x\text{Ga}_{1-x}\text{As}$ QW samples started with a GaAs buffer grown at 580°C followed by a 10-nm-thick $\text{In}_x\text{Ga}_{1-x}\text{As}$ (where $x = 0.18$) layer grown at 485°C . Finally, a 20-nm-thick GaAs cap layer were grown at 485°C .

The PL spectra were measured by using a laser ($\lambda = 514\text{ nm}$) as the excitation source. The Raman spectroscopy was

done using RENISHAW INVIA Raman microscope RE-04.

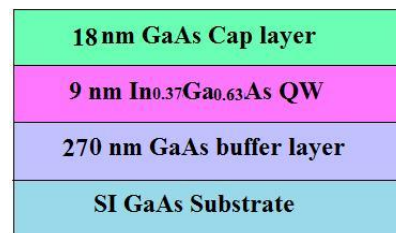


Fig. 1: The schematic structure of the sample.

3. Results and Discussion

The temperature-dependent PL spectra were carefully measured from 15 K to 300 K as shown in Fig. (2). For each sample at a specific temperature, one peak is observed.

The temperature-dependent PL peak energies of the samples show quite similar behavior in the whole temperature range from 15 K to 300 K. The temperature-dependent integrated photoluminescence intensities of the samples reveal that the photoluminescence intensity is significantly enhanced by about 24 times at 15 K with respect to that at 300 K for sample MBE 1338 (Indium 18%); about 20 times at 15 K with respect to that at 300 K for sample MBE 1344 (Indium 09%) and about 9 times at 15 K with respect to that at 300 K for sample MBE 1340 (Indium 37%). In all the 3 samples there is a red shift of about 81meV.

Fig. (3) shows the concentration dependence of PL spectrum. It is observed that as the concentration of indium in $\text{In}_x\text{Ga}_{1-x}\text{As}$ increases the intensity goes on

*Corresponding author: LaxmanSurvase

increasing and there is a red shift of about 300 meV for the spectra at temperatures 15 K and 100 K. It is observed that there is no intensity peak for the indium concentration 9% at 300 K. There is a shift of about 170 meV between the other two concentrations (18 and 37 %) at 300 K.

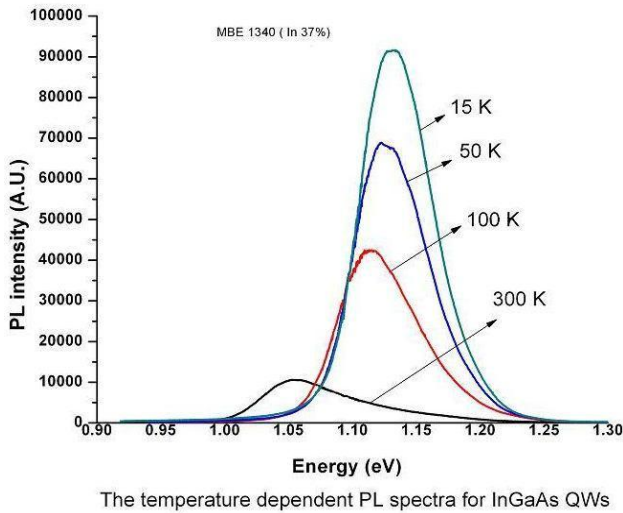


Fig. 2 Temperature-dependent PL spectra measured from 15 K to 300 K

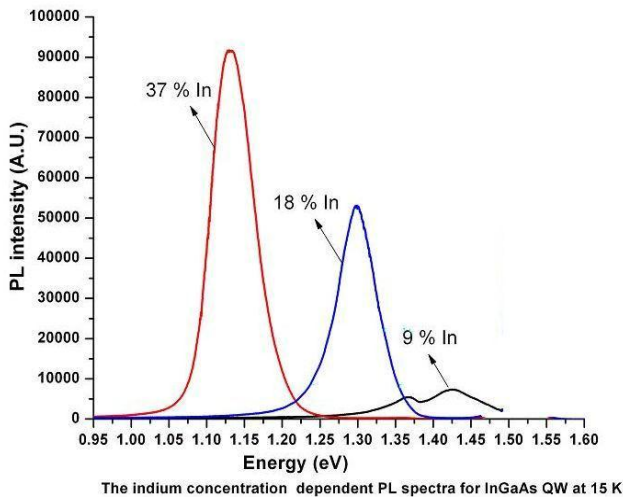


Fig. 3 Concentration dependence of PL spectrum

The samples investigated by PL were studied then by Raman scattering technique. The Raman spectrum for the samples is shown in Fig. (4).

The spectra have been recorded at room temperature for indium contents 10 %, 18%, 30 % and 37%. The Raman spectra for the sample show a strong line at 292.6 cm^{-1} corresponding to scattering by longitudinal-optical LO GaAs phonons. There is also a weaker line at 268.527 cm^{-1} corresponding to scattering by transverse-optical TO GaAs phonons. It is observed that as there is no change in the thickness of the QW (~ 10 nm) there is no horizontal shift in the spectrum. But it is observed that as the Indium percentage goes on increasing there is a vertical shift. i.e the intensity of the weaker peak goes on decreasing with the increase in percentage of Indium content.

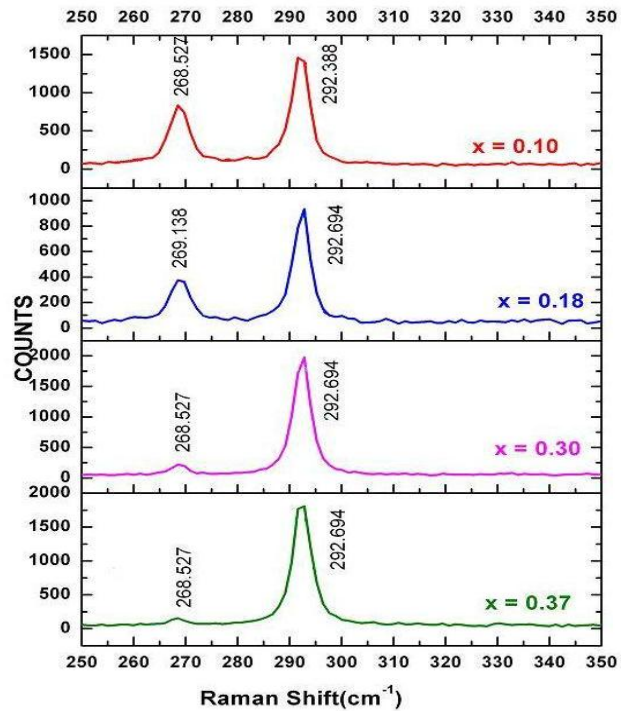


Fig.4 Raman spectrum for the samples

Table 1 Observed and reported Raman peaks for $alnGaAs$ QW

| Peak | Observed energy cm^{-1} | Closest Reported Energy cm^{-1} | Phonon mode | Designation | |
|------|---------------------------|-----------------------------------|-------------|-------------|--|
| 1 | 292.64 | 292 | GaAs like | LO | In _{0.37} Ga _{0.63} As |
| 2 | 268.527 | 266.3 | GaAs like | TO | In _{0.37} Ga _{0.63} As |

The reported value of peak is taken from the paper as mentioned in reference paper [Nishida *et al* 2002] and peak two from reference paper [Mazur *et al* 2006].

Conclusion

In conclusion, $In_xGa_{1-x}As$ QW structures have been grown by molecular beam epitaxy and investigated by temperature-dependent PL measurements from 15 K to 300 K. The temperature-dependent integrated photoluminescence intensities of the samples reveal that the photoluminescence intensity is significantly enhanced. It is observed that as the concentration of indium in $In_xGa_{1-x}As$ increases the intensity goes on increasing. The Raman spectra for the sample show a strong line at 292.6 cm^{-1} corresponding to scattering by longitudinal-optical LO GaAs phonons. There is also a weaker line at 268.527 cm^{-1} corresponding to scattering by transverse-optical TO GaAs phonons.

Acknowledgement

We would like to acknowledge Dr. chalpati director optoelectronic division. SAMEER, IIT Mumbai. and Dr. A.M Narsale Ex-Director WRIC Mumbai for his guidance.

We would also like to thank and Mr. AbhijeetBhogale of University of Mumbai for his help in characterization.

References

- Devaux F, Chelles S, Ougazzaden A, Mircea A, Harmand J C (1995), Electro-absorption modulators for high-bit-rate optical communications: a comparison of strained InGaAs/InAlAs and InGaAsP MQW, *Semiconductor Science and technology* Vol-10, pp.887-901
- Raisky O Y, Wang W B, Alfano R R, Reynolds C L, Stampone Jr D V, Focht M W (1993), $In_{1-x}Ga_xAs_{1-y}P_y/InP$ multiple quantum well solar cell structures, *Journal of Applied Physics* Vol-10, pp. 5790-5794
- Levine B F,(1993), Quantum well infrared photodectors, *Journal of Applied Physics* Vol-8 pp. 71-81.
- B.M. Arora, Sandip Ghosh, Shouvik Datta, Shailendra Kumar(2001) Recent developments in spectroscopy of quantum structures, *Materials Science in Semiconductor Processing* Vol-4 ,pp 489–495
- Y. F. Chen, J. L. Shen, and L. Y. Lin. (2009) Journal of Applied. Physics Photothermal luminescence spectroscopy of GaAs/AlGa_{1-x}As_x Vol-73 pp 4555-4559.
- K.Nishida, S.Hagiwara,M.Teranishi,O.Sirakawa,A.Hirakai (2002)Effects of the number of periods on strain in superlattices *Journal of Applied. Physics* Vol-91, pp 5155-5157
- Yu. I. Mazur, Zh. M. Wang, and G. J. Salamo *et al* (2006) ,Investigation of indium distribution in InGaAs/ GaAs quantum dot stacks using high-resolution x-ray diffraction and Raman scattering *Journal of Applied. Physics*Vol- 99 pp 023517-01 to 10.